


ALL BLACK INSTALLATION PROCESS

AUTO GLASS REPLACEMENT

INSTALLATION GUIDELINE

1

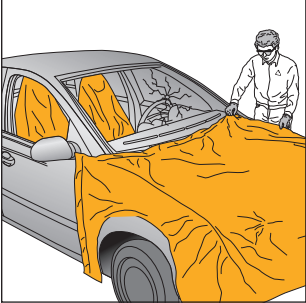

- Wear personal protective equipment
- Cover parts to be protected
- Use seat covers

2



- Carefully remove all trims and accessories
- Carefully remove ADAS related sensors and cameras

3



- Cut out damaged windshield using Sika® SmartCut, electrical knife, cutting wire, cold knife etc.
- Remove dirt with a vacuum cleaner or brush

4




- Remove the damaged windshield

5




- Remove debris with a vacuum cleaner or brush
- Clean the entire aperture with Sika® Cleaner G+P, making sure the surface is completely dry and no moisture remains

6

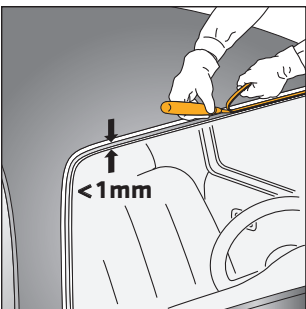

- Trim back the remaining PUR bead and try to cause as little damage as possible
- The remaining PUR must be under 1 mm before it is safe to apply fresh adhesive

7

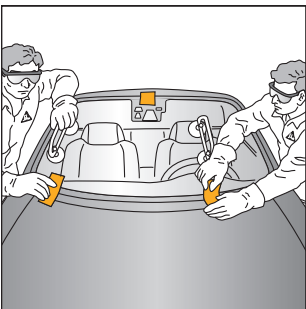


- Dry fit the windshield
- To ensure a quick and precise installation of the windshield once the adhesive is applied, add fitting marks

8




- Clean the windshield with Sika® Cleaner G+P and check for contamination
- If contaminated, scrub the bonding surface with Sika® Cleaner PCA
- Wipe the window dry with a paper towel

9

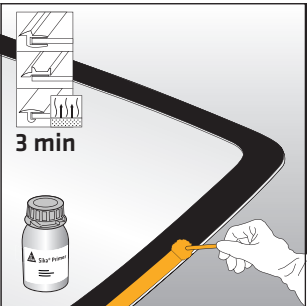


- Use a dauber or Sika® Cleaner PCA stick as applicator
- Prime the bonding surface of the glass using Sika® Primer-207 or Sika® Primer-507
- Tightly close the can immediately after use
- Allow to flash-off for at least 3 minutes

10

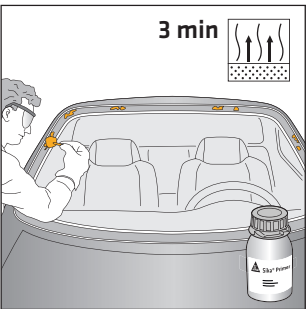

- Cover any minor damage to paint work using Sika® Primer-207 or Sika® Primer-507
- Tightly close the can immediately after use
- Allow to flash-off for at least 3 minutes
- In case of larger areas, contact a paint shop or refer to the car manufacturer's specification

11

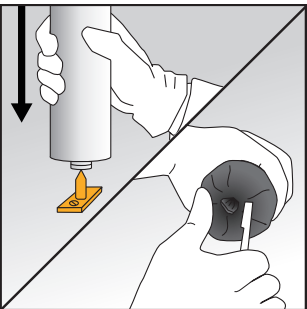


- Cartridge: open by piercing the membrane
- Unipack: open by simply slicing the end of the unipack approx. 1 cm between the clip and the shoulder. Avoid the foil weld
- PowerCure: charge the Dispenser, no need to open manually

12



- Prepare a "V" notched nozzle that has the same height as the pinchweld mounting surface and the roof of the car
- Apply a triangular bead of adhesive either to the glass or the aperture.
- It is important that the adhesive matches both the primed surface on the glass and the fresh cut bead of urethane

13

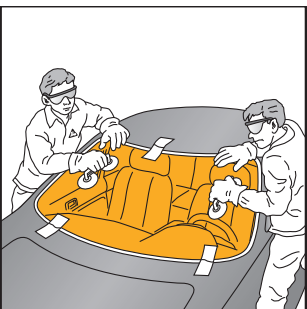


- Place the windshield in position within the open time of the adhesive
- Caution: the open time may be significantly shorter at elevated temperature

14



- Remount trim and moldings so that they fit properly, secure all cowlings under the bonnet and affix wipers
- Ensure that all dismantled parts are installed correctly
- Refit and rear-view mirror and check if all ADAS related sensors and cameras work correctly

15

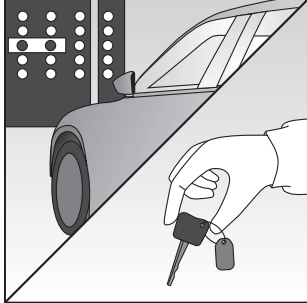

- Conduct and record ADAS recalibration according OEM specification
- Record all batch numbers on job card to insure full traceability
- Complete paperwork and hand back keys to customer after the minimum safe drive-away time is achieved



BONDING SURFACE	SURFACE PREPARATION STEPS
Float Glass and Ceramic coated Glass ^a	●
Bare Metal Scratch < 5 cm ²	●
Bare Metal Scratch < 150 cm ²	●●
Intact OEM Paint	●
Repair Paint (after complete curing of paint) ^b	●
PVC/RIM Encapsulation, Pre-applied Adhesive System ^b	●
Fresh Cut Bead	- / ● Optional
Pre-applied OEM Primer	●
PC / PMMA glass ^c	●

● = Sika® Primer-207 or Sika® Primer-507

a) Windshield must be clean of dirt and dust. Potential contamination must be removed by wet scrubbing with Sika® Cleaner PCA

b) Scuff surface

c) Anti Scratch Coating must be removed prior to use, scuff surface, (only for temporary glazing, UV-protection required)

Our most current General Sales Conditions shall apply. Please consult the most current local Product Data Sheets prior to any use.

www.sika.com/aftermarket

BUILDING TRUST



Sika Services AG / Industry / Aftermarket / All Black Installation Process / TZ / 02.2022